



## Full Length Article

## Graphene oxide/mixed metal oxide hybrid materials for enhanced adsorption desulfurization of liquid hydrocarbon fuels



Robert Menzel<sup>a,c,\*,1</sup>, Diana Iruretagoyena<sup>b,\*,1</sup>, Yifan Wang<sup>a</sup>, Salem M. Bawaked<sup>d,e</sup>, Mohamed Mokhtar<sup>d,e</sup>, Shael A. Al-Thabaiti<sup>d,e</sup>, Sulaiman N. Basahel<sup>d,e</sup>, Milo S.P. Shaffer<sup>a</sup>

<sup>a</sup> Department of Chemistry, Imperial College, London SW7 2AZ, UK

<sup>b</sup> Department of Chemical Engineering, Imperial College, London SW7 2AZ, UK

<sup>c</sup> Bio Nano Consulting, The Gridiron Building, One Pancras Square, London N1C 4AG, UK


<sup>d</sup> Department of Chemistry, Faculty of Science, King Abdulaziz University, Jeddah, Saudi Arabia

<sup>e</sup> Surface Chemistry and Catalytic Studies Group, King Abdulaziz University, Jeddah, Saudi Arabia

## HIGHLIGHTS

- Sulfur uptake using MMOs supported on GO was studied for the first time.
- Sulfur uptake and stability of MMOs is enhanced by the presence of GO.
- GO-MMOs show good selectivity for organosulfur compounds over sulfur-free aromatics.

## GRAPHICAL ABSTRACT

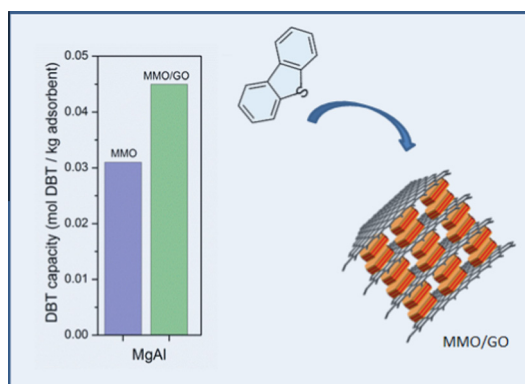

## ARTICLE INFO

## Article history:

Received 6 March 2016

Received in revised form 21 April 2016

Accepted 26 April 2016

## Keywords:

Graphene oxide  
Mixed metal oxide  
Dibenzothiophene  
Adsorption  
Desulfurization

## ABSTRACT

A series of mixed metal oxides (MMOs) adsorbents (MgAl-, CuAl- and CoAl-MMOs) were supported on graphene oxide (GO) through in-situ precipitation of layered double hydroxides (LDHs) onto exfoliated GO, followed by thermal conversion. The study shows that GO is an excellent support for the LDH-derived MMOs due to matching geometry and charge complementarity, resulting in a strong hybrid effect, evidenced by significantly enhanced adsorption performance for the commercially important removal of heavy thiophenic compounds from hydrocarbons. Fundamental liquid-phase adsorption characteristics of the MMO/GO hybrids are quantified in terms of adsorption equilibrium isotherms, selectivity and adsorbent regenerability. Upon incorporation of as little as 5 wt% GO into the MMO material, the organosulfur uptake was increased by up to 170%, the recycling stability was markedly improved and pronounced selectivity for thiophenic organosulfurs over sulfur-free aromatic hydrocarbons was observed.

© 2016 Elsevier Ltd. All rights reserved.

\* Corresponding authors. Present address: School of Chemistry, University of Leeds, Leeds LS2 9TJ, UK (R. Menzel).

E-mail addresses: [R.Menzel@leeds.ac.uk](mailto:R.Menzel@leeds.ac.uk) (R. Menzel), [d.iruretagoyena09@imperial.ac.uk](mailto:d.iruretagoyena09@imperial.ac.uk) (D. Iruretagoyena).

<sup>1</sup> These authors contributed equally to the work.

## 1. Introduction

Exfoliated graphene has attracted enormous attention due to its unique combination of extraordinary properties [1]. Among intense research activity across many disciplines [2], the utilization

of graphene-related materials as support frameworks for functional nanoparticles has emerged as a promising research area, utilizing a combination of properties such as high specific surface area, light weight, chemical inertness, mechanical robustness and excellent electrical and thermal conductivity. Hybrid materials based on inorganic nanoparticles and graphene or its hydrophilic derivative, graphene oxide (GO), have been shown to significantly boost the functional performance in a wide range of applications [3], such as heterogeneous [4], electro- [5] and photo-catalysis [6], energy storage [7], CO<sub>2</sub> adsorption [8], and sensing [9].

This study focuses on the utilization of GO as support for two-dimensional functional nanoparticles, specifically for mixed metal oxides (MMOs) that are produced from two-dimensional layered double hydroxide (LDH) nanoparticles. GO is expected to be particularly efficient as a support for LDH-derived MMOs due to the matching 2D geometry and the charge complementarity of the initial (positively-charged) LDH nanoplatelets and the exfoliated (negatively-charged) GO sheets. The functionality of the resulting MMO/GO hybrids is assessed for the commercially important adsorption of thiophenic organosulfur contaminants from hydrocarbons, the first example of applying inorganic GO hybrids to adsorption from non-aqueous systems.

Molecular adsorption from the liquid phase onto solid state adsorbents is a key step in many large-scale processes, including purification and liquid separation technologies. However so far, liquid-phase adsorption studies involving graphene and its derivatives have mainly focused on water purification, e.g. the removal of toxins, such as heavy metal ions [10], oxyanions, dyes and organic pollutants from aqueous systems [11]. In this context, most studies have dealt with pure graphene and GO powders [11], and, recently, graphene aerogels [12,13] where non-specific adsorption is usually prevalent. One approach to improve adsorption selectivity and capacity is the introduction of specific functional groups to the graphitic surface, for example via chemical functionalization of GO with thiol groups for the selective and efficient removal of Hg<sup>2+</sup> ions from water [14]. A small number of studies have also explored the potential of metal-oxide/GO hybrids for enhancing adsorption from aqueous systems. Flower-like TiO<sub>2</sub> nanostructures grown on GO were shown to be efficient, but non-specific adsorbents of heavy metal ions [15]. Further, iron-oxide/GO composites have been investigated for the removal of organic dyes [14] and arsenates [16,17] from water.

In this paper, the removal of sulfur-containing aromatics, such as dibenzothiophene (DBT), from hydrocarbons is investigated. Organic sulfur derivatives are major contaminants in petroleum and a source of SO<sub>x</sub> emission, which results in air pollution, acid rain and catalyst poisoning issues [18]. Currently, the most widely employed desulfurization technology for petroleum derived hydrocarbons is the hydrodesulfurization (HDS) process. However, for heavy thiophenic derivatives, such as DBT and its substituted derivatives, desulfurization via HDS is slow and inefficient [19,20]. Selective adsorption desulfurization provides a promising, alternative approach for removing thiophenic derivatives from hydrocarbon fuels with the potential to achieve low sulfur levels at relatively low environmental impact. There are two main types of adsorption desulfurization processes: reactive adsorption that occurs at high temperature and, non-reactive adsorption operating at <100 °C. In the latter case, the organosulfur compounds are adsorbed as unchanged molecular species on the surface, simplifying the regeneration and cycling of the adsorbent. A range of adsorbent materials are currently under study, including zeolites [21], metal organic frameworks (MOF) [22], mixed metal oxides [18], activated carbon [23,24], and molecularly imprinted polymers [25]. In general, the development of a scalable adsorbent composed of inexpensive materials, but possessing a large capacity and the

ability to regenerate for a significant number of cycles, would be ideal for continuous operation in a desulfurization unit [18].

In this paper, readily available, cost-effective LDH-derived MMOs are investigated which have been shown to be effective adsorbents due to their basic character that generates acid-base Lewis interactions with the organic molecules [26]. In addition, MMOs show promising features for adsorption due to their regenerability and adjustable elemental composition [18]. In this study, MgAl-LDH, a cost effective and well-studied LDH compound, was loaded with small weight fractions of GO, followed by thermal conversion into MgAl-MMO/GO hybrids. The pure and hybrid MgAl-MMO materials were tested in batch experiments to assess the non-reactive adsorption of dibenzothiophene (DBT) from dodecane, a typical heavy organosulfur contaminant of petroleum. Crucial adsorption parameters such as DBT uptake capacity, adsorption equilibrium isotherms and DBT selectivity in the presence of sulfur-free aromatics, as well as the adsorbent recyclability were quantified. In order to validate the findings of the MgAl-MMO model system, two other MMO systems with altered chemical composition were synthesized, based on the substitution of Mg<sup>2+</sup> ions by sulfur-affine Cu<sup>2+</sup> and Co<sup>2+</sup> ions, that have the potential to strongly bind aromatic organosulfur compounds via sulfur-metal  $\sigma$ -bonds and  $\pi$ -interactions [27,28].

## 2. Results and discussion

### 2.1. Synthesis of MMO/GO hybrids

MgAl-MMO can be easily synthesized from cheap reagents through straightforward co-precipitation of MgAl-LDH at basic conditions, followed by simple thermal conversion into MgAl-MMO. The parent CuAl-LDH and CoAl-LDH materials required slightly more complex synthesis approaches, namely co-precipitation at constant pH and slow, urea-mediated co-precipitation under inert conditions, respectively [29]. Incorporation of GO is easily achieved for all three co-precipitation methodologies through simple addition of GO to the basic precipitation medium. The basic pH of the precipitation medium promotes the deprotonation of carboxylic acid groups at the GO surface, facilitating the exfoliation of GO into individual nanosheets through electrostatic stabilization. Further, the negatively-charged carboxylate groups on the GO sheets form ideal nucleation sites for the formation of the positively-charged LDH nanocrystals. These effects facilitate the full utilization of the high surface area of the GO, resulting in an intimate mixture of the GO and LDH nanostructures on the nanoscale. For this study, hybrid materials were loaded with only 5 wt% GO, identified as the optimum nanocarbon loading to enhance the CO<sub>2</sub> storage performance [30,31]. Considering, the order-of-magnitude difference between the theoretical specific surface area of fully exfoliated GO (~2650 m<sup>2</sup>/g) and the measured specific surface area of the MgAl-MMO nanoparticles (135 m<sup>2</sup>/g, Table 1), small quantities of the more expensive GO should be sufficient to promote the formation of true hybrid materials.

### 2.2. Materials characterization

The bulk chemical composition of the synthesized pure MgAl-MMO and the MgAl-MMO/GO hybrid was determined by ICP-OES, confirming the presence of Mg<sup>2+</sup> and Al<sup>3+</sup> in ratio of 2.2:1 for both materials (Table 1). This ratio is very close to the nominal molar ratio (2:1) of the original metal salts and shows that the presence of GO during synthesis does not affect the elemental MMO composition significantly. In all the adsorbents, sodium was detected only at trace levels by ICP, indicating that the NaOH and Na<sub>2</sub>CO<sub>3</sub> used during the synthesis were successfully removed.

**Table 1**


Chemical composition and textural characterization of the MMO and MMO/GO adsorbents.

Sample name	GO loading (wt%) <sup>a</sup>	Metal:Al ratio <sup>b</sup> (mol:mol)	S <sub>BET</sub> <sup>c</sup> (m <sup>2</sup> /g)	V <sub>pore</sub> <sup>e</sup> (cm <sup>3</sup> /g)
MgAl-MMO	0	2.20	135	0.52
MgAl-MMO/GO	4	2.20	195	0.57
CuAl-MMO	0	2.50	53	0.13
CuAl-MMO/GO	3	2.60	56	0.15
CoAl-MMO	0	1.90 <sup>d</sup>	65	0.12
CoAl-MMO/GO	3	1.60 <sup>d</sup>	85	0.20

<sup>a</sup> As determined by TGA.<sup>b</sup> As determined by ICP-OES.<sup>c</sup> Specific surface area as determined by nitrogen adsorption.<sup>d</sup> Determined by XPS.<sup>e</sup> Mesopore volume as determined by nitrogen adsorption.


SEM imaging (Fig. 1a) indicates that the initially precipitated MgAl-LDH nanoparticles are present as small, thin individual nanoplatelets, suggesting a good geometric match between the two two-dimensional components in the initial MgAl-LDH/GO hybrid. After thermal conversion, SEM showed that aggregates of very small MMO particles had formed (Fig. 1b); the exact size and shape of the individual MMO nanoparticles cannot be discerned due to the resolution limitation of the SEM. It is noteworthy that SEM fails to visualize any indication for GO in the hybrid materials (Fig. 1a and b), suggesting the presence of well-exfoliated GO sheets, fully covered by the functional nanoparticles.

TGA in oxidative air atmosphere was used to estimate the actual GO content of the MgAl-LDH/GO adsorbent (Fig. 2a). The smaller TGA residue weight of the hybrid materials compared to pure MgAl-MMO, indicated the presence of combustible nanocarbons in the hybrid adsorbent; simple, rule-of-mixture analysis of the residue values suggests a carbon content of about 4 wt% (Table 1). This slightly lower value compared to the nominal GO weight fraction (5 wt%) is consistent with the loss of highly oxidized polyaromatic debris present in the original GO material but known to be solubilized and removed under the basic conditions of the LDH/GO synthesis and washing [32]. Powder XRD shows

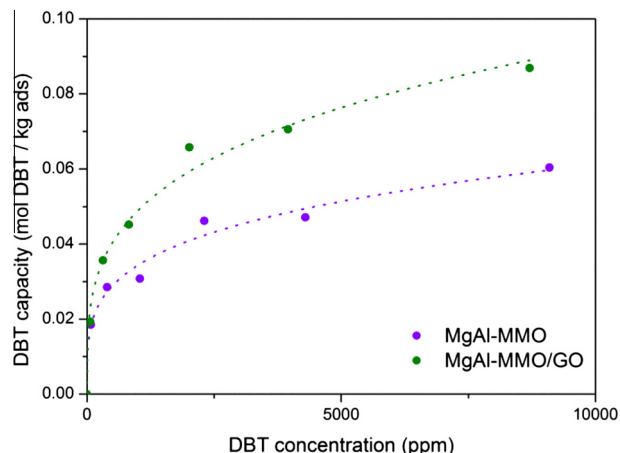

**Fig. 2.** Adsorption equilibrium isotherms for the liquid-phase adsorption of DBT in dodecane solution onto MgAl-MMO and MgAl-MMO/GO, respectively; the dotted lines indicate isotherm fits according to the Freundlich model. Temperature 323 K.

that the MgAl-LDH and MgAl-LDH/GO parent materials are phase-pure, exhibiting the typical diffractions of hydrotaalcite-like compounds (Fig. 1d). Upon thermal conversion, the pure and hybrid material show the typical diffractions of periclase-type MMOs (Fig. 1e). Analysis of the broadening of the (200) peaks yields very similar crystal domain sizes for the pure and hybrid MgAl-MMO materials (3.4 and 3.3 nm respectively), indicating that GO incorporation has no significant impact on the crystallinity of the MMO adsorbent. It is noteworthy that no diffraction features related to GO are observed, most likely due to the small loading fraction of GO, its relative disorder, and its high degree of exfoliation. Nitrogen adsorption measurements, however, reveal differences between the pure MMO and hybrid MMO/GO adsorbents. Nitrogen adsorption and desorption follow a clear Type IV isotherm shape, typical for mesoporous materials with strong adsorbate-adsorbent interactions (Fig. 1f). Previous studies showed that the incorporation of GO is a simple route to increase the specific

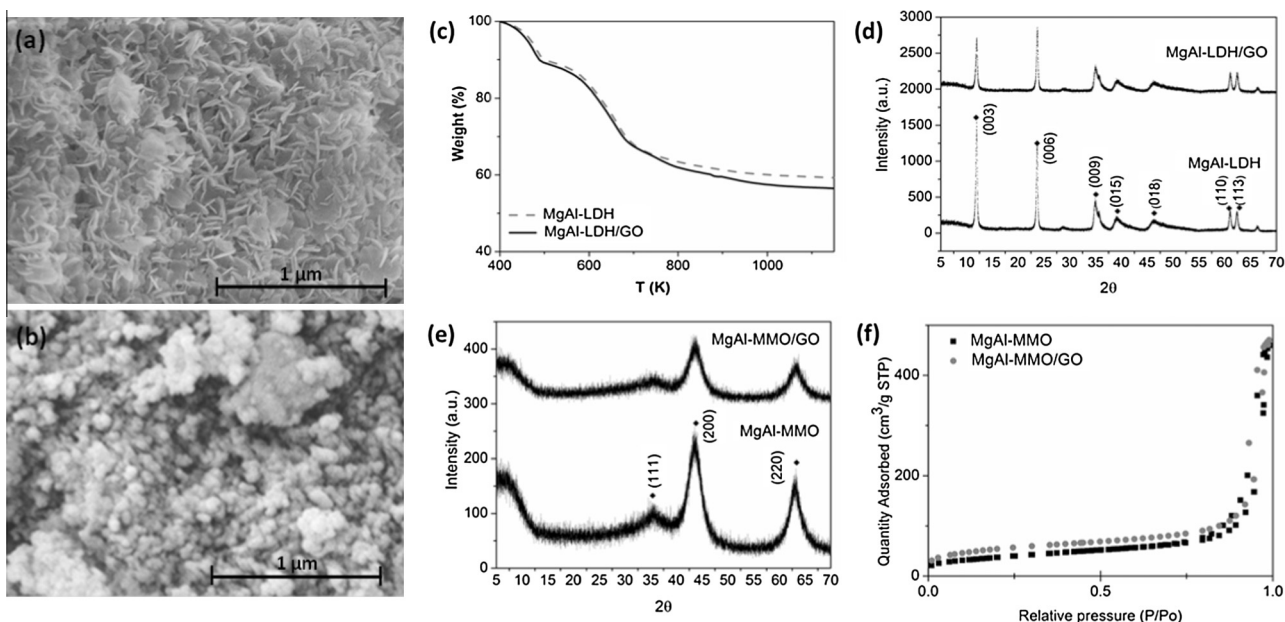

**Fig. 1.** Materials characterization. (a) SEM of the as-synthesised LDH/GO hybrid; (b) SEM image of thermally-converted MMO/GO hybrid; (c) thermograms of MgAl-LDH and MgAl-LDH/GO; (d) XRD diffraction patterns of MgAl-LDH/GO and MgAl-LDH; (e) XRD diffraction patterns of MgAl-MMO/GO and MgAl-MMO; (f) N<sub>2</sub> adsorption equilibrium isotherms of MgAl-MMO and MgAl-MMO/GO.

surface area of LDHs and MMOs, although other means are possible [8]. In this study, the inclusion of 4 wt% GO in the hybrid material leads to an increase in specific surface area, as determined by BET analysis, by more than 40% (Table 1). This observation confirms the formation of a true MMO/GO hybrid material. Similarly to the MgAl-MMO system, the incorporation of 5 wt% GO into CuAl-MMO and CoAl-MMO also leads to increases in specific surface area (Table 1).

### 2.3. Liquid-phase DBT adsorption

The liquid-phase adsorption properties of the MgAl-MMO and MgAl-MMO/GO materials were assessed through batch adsorption experiments at 323 K, based on exposure of the adsorbent powders to dilute DBT solutions in dodecane for 5 days. The adsorption equilibrium isotherms measured in a concentration range between 250 and 10,000 ppm DBT clearly demonstrate marked enhancement of DBT uptake upon incorporation of GO into the MMO adsorbent (Fig. 2). At all DBT concentrations studied, DBT adsorption onto the MgAl-MMO/GO hybrid is significantly larger than adsorption onto the pure MgAl-MMO. For both pure and hybrid adsorbent, the experimental data were adequately described by the Freundlich isotherms indicating DBT sorption onto a heterogeneous MMO surface. The Freundlich parameters of both materials were found to be similar indicating that the presence of GO does not modify significantly the nature of the adsorption sites (ESI, Table S2). It is worth noting that pure (thermally-treated) GO did not adsorb any detectable DBT (ESI, Table S3). Further, a simple physical mixture of MgAl-MMO with 5 wt% GO exposed to 1500 ppm DBT showed virtually identical adsorption capacity as the pure MgAl-MMO (0.031 mol DBT/kg MMO). These controls confirm that the intimate mixture of LDH particles and GO sheets during the in-situ synthesis process is a prerequisite for the increased DBT capacity, resulting in the formation of a true hybrid material that clearly outperforms its individual components. This intimate mixture of the components allows for maximum utilization of the large surface area and negative surface charge of the GO. Exfoliated GO sheets can therefore act effectively as spacers between individual MMO particles, enhancing overall particle dispersion and significantly improving accessibility to the adsorption sites.

The regeneration of the MgAl-MMO and MgAl-MMO/GO hybrid was assessed by carrying out 5 multicycle tests (ESI, Fig. S1). The spent adsorbents were regenerated by washing with dodecane at 373 K. Then the MMOs were centrifuged, recovered, dried and exposed again to 1500 ppm DBT at 323 K. The unsupported adsorbent reduced its initial capacity by 10% in the first cycle and then remained constant over 5 adsorption-desorption cycles. On the other hand, the hybrid lost only 2% of its initial capacity in the first cycle and then its capacity remained stable. The improved stability of the supported material is consistent with observations of improved thermal cycling stability of MgAl-MMO/GO adsorbents used for CO<sub>2</sub> adsorption. Similarly to the CO<sub>2</sub> adsorption case, the improved DBT regeneration stability is due to the robust anchoring of the MMO particles on the exfoliated GO, preventing sintering of the small MMOs particles during DBT desorption at increased temperatures and during drying of the regenerated adsorbent materials.

In order to test the generality of the GO-hybrid enhancement, the DBT uptake (at an intermediate initial DBT concentration of 1500 ppm) was also tested over CuAl-MMO/GO and CoAl-MMO/GO adsorbents (Fig. 3, Table 2). The batch adsorption measurements clearly showed that the incorporation of small GO quantities markedly enhances the DBT uptake for all three MMO systems.

The DBT capacity per mass of MMO and per total mass of adsorbent of the transition-metals is lower than for the MgAl-MMOs.

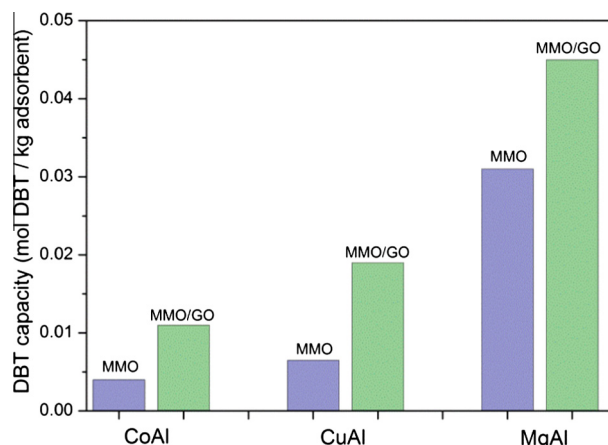


Fig. 3. DBT uptake from dodecane (initial DBT concentration 1500 ppm) by CoAl-MMO, CuAl-MMO and MgAl-MMO in their pure (MMO) and hybrid (MMO/GO, containing 5 wt% GO) form.

Table 2

DBT uptake from dodecane (initial DBT concentration 1500 ppm, adsorption temperature 50 °C) by MgAl-MMO/GO, CuAl-MMO/GO and CoAl-MMO/GO hybrids.

Sample name	mol DBT/kg MMO <sup>A</sup>	mol DBT/kg ads <sup>B</sup>	mg S/g ads <sup>B</sup>	μmol DBT/m <sup>2</sup> ads <sup>B</sup>
MgAl-MMO	0.0308	0.0308	0.987	0.228
MgAl-MMO/GO	0.0471	0.0452	1.449	0.232
CuAl-MMO	0.0065	0.0065	0.209	0.123
CuAl-MMO/GO	0.0192	0.0187	0.598	0.333
CoAl-MMO	0.0042	0.0042	0.133	0.064
CoAl-MMO/GO	0.0111	0.0107	0.344	0.126


<sup>A</sup> Intrinsic adsorption capacity of the MMO component, i.e. uptake per kg MMO.

<sup>B</sup> Total adsorption capacity of the adsorbent (ads), i.e. uptake per total adsorbent weight (kg MMO + kg GO).

However, when the uptake is normalized by surface area of the adsorbents (Table 2), the CuAl-MMO/GO shows the highest capacity. Analogous trends have been found for MOFs and zeolites when the effect of different transition metals was investigated [27,28]. The adsorption capacities per mass of total adsorbent presented in this study are comparable to values reported for some zeolites (~0.3–3 mg S/g ads) when differences in concentration and temperature are taken into account [27]. However, they are lower than those reported for some activated carbons and MOFs materials (~5–20 mg S/g ads), which have much higher specific surface area [28,33]. The fact that MMOs show adsorption capacities per m<sup>2</sup> of the same order of magnitude to those obtained for MOFs suggests that the capacity of MMOs (and in particular MMO/GO hybrids) can be enhanced by further increasing their intrinsic surface area. Therefore, the challenge is to find alternative methods to synthesize MMOs with smaller particle sizes, in particular for the CuAl- and CoAl-MMOs. It is worth noting that, in the transition-metal containing MMO systems, the large increase in DBT uptake per unit area upon GO incorporation (up to 170% in the case of the CuAl-MMO/GO hybrid, Table 2) cannot be explained by an increase in available MMO surface area alone. In these adsorbents, GO appears to exhibit additional functionality, most likely associated with the generation and stabilization of otherwise labile, highly-active adsorption sites. Further studies to elucidate the underlying, mechanistic details and to fully utilize this GO functionality for further organosulfur adsorption enhancement are currently underway.

An important practical aspect in the context of liquid hydrocarbon fuel purification is the impact of sulfur-free aromatics on the DBT uptake. Conventional, non-specific adsorbents, such as activated carbons, have been observed to show reduced DBT capacity



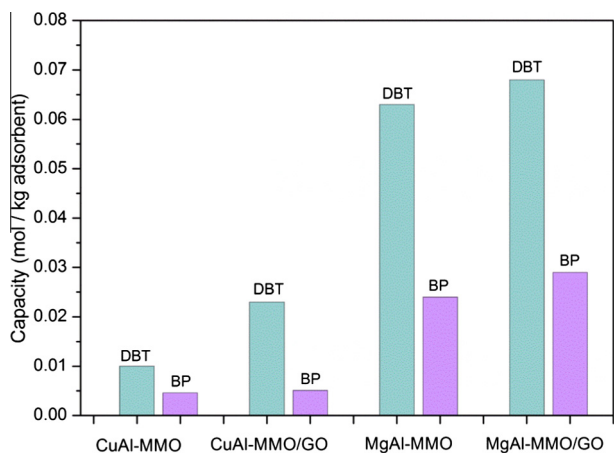

**Fig. 4.** DBT adsorption capacity in the presence of BP: DBT and BP uptakes from dodecane solution, containing 1500 ppm DBT and 1500 ppm BP, by pure and hybrid CuAl-MMO and MgAl-MMO adsorbents.

in the presence of pure hydrocarbon aromatics due to competitive adsorption. As a model for the influence of aromatics, the uptake of DBT in the presence of biphenyl (BP), a structurally similar aromatic hydrocarbon, was measured for both MgAl-MMO and CuAl-MMO systems. While adsorption of DBT and BP occurred simultaneously (Fig. 4), BP uptake was significantly smaller and did not compete with or inhibit DBT uptake. In fact, for all the adsorbent systems, the DBT uptake in presence of equimolar concentrations of BP (Fig. 4) remained as high as the uptake from DBT-only dodecane solution (Fig. 3). These results confirm a marked affinity and selectivity toward sulfur-containing compounds, most clearly observed for the CuAl-MMO/GO adsorbent.

### 3. Conclusions

The non-reactive adsorption performance of GO-containing inorganic hybrid materials for sulfur-removal from liquid hydrocarbons was studied for the first time, by investigating DBT adsorption from a dodecane solution onto MgAl-, CuAl-, and CoAl-MMO adsorbents. Synthesis of true hybrid MMO/GO adsorbents was achieved through in-situ precipitation of LDH particles onto exfoliated GO sheets, followed by thermal conversion. In these MMO hybrid materials, small quantities of GO likely act as effective spacer between the adsorbent particles, leading to improved accessibility of active adsorption sites, resulting in significantly enhanced organosulfur uptake. These improvements are unaffected by the presence of a typical fuel components (BP), indicating a robust selectivity for sulfur-containing aromatics. Additionally, the cycle stability of the pure MMO was enhanced by the addition of GO, due to robust binding between the charge-complementary hybrid components, inhibiting MMO particle sintering during adsorbent regeneration.

The adsorption capacities per  $m^2$  are highest for the CuAl-MMO/GO system, reflecting the combined benefits of GO incorporation and the enhanced sulfur-affinity of the Cu-substituted MMO system. Further, our adsorption results suggest that GO incorporation into CoAl-MMO and CuAl-MMO leads to a significant change in DBT adsorption mechanism, suggesting that the GO component performs an additional function in transition-metal containing MMO systems. Higher absolute organosulfur capacities (per mass adsorbent) may therefore be accessible through improved understanding and utilization of the adsorption mechanism of sulfur-containing aromatics onto transition-metal MMO/GO adsorbents and by finding methods to synthesize copper-containing MMO

adsorbents with higher intrinsic surface areas; for the latter option, GO-support might provide additional crucial benefits by stabilising smaller, otherwise labile adsorbent nanoparticles.

Beyond the direct relevance to petroleum purification, the consistent improvements in DBT adsorption across the three hybrid adsorbent systems studied demonstrate the general benefit of using a small proportion of well exfoliated graphene oxide as a two dimensional, charged support for other two dimensional functional materials, representing a broad class of possible future hybrids. Importantly, the study is also an example for the direct utilization of specific GO properties such as facile exfoliation in aqueous base solution, 2D geometry and negative surface charge, rather than considering GO as an aggressive route to imperfect graphene. Further, the findings highlight the need for thorough synthetic approaches to fabricate true hybrid materials for maximum performance enhancement. These outlined principles provide a basis for the development of sulfur-compound adsorbents with higher capacities and are likely to be relevant to a number of other GO-hybrid materials applications where adsorption from liquid hydrocarbons is a crucial step, such as liquid-liquid separation or fine-chemical synthesis via heterogeneous catalysis.

### Acknowledgements

The authors are grateful to Prof D. Chadwick for advice. R.M. acknowledges financial support from the Deanship of Scientific Research at King Abdulaziz University (Grant D/05/432) and D.I. from EPSRC (UK) Grant EP/K014749/1. This research was also sponsored by EPSRC (UK) Grant EP/K01658X/1.

### Appendix A. Supplementary material

Supplementary data associated with this article can be found, in the online version, at <http://dx.doi.org/10.1016/j.fuel.2016.04.125>.

### References

- [1] Geim AK. Graphene: status and prospects. *Science* 2009;324:1530–4.
- [2] Ahn J-H, Hong BH. Graphene for displays that bend. *Nat Nano* 2014;9:737–8.
- [3] Shearer CJ, Cherevan A, Eder D. Application and future challenges of functional nanocarbon hybrids. *Adv Mater* 2014;26:2295–318.
- [4] Celaya-Sanz A, Morales-Vega N, De Marco M, Iruretagoyena D, Mokhtar M, Bawaked SM, et al. Self-condensation of acetone over Mg–Al layered double hydroxide supported on multi-walled carbon nanotube catalysts. *J Mol Catal A: Chem* 2015;398:50–7.
- [5] Xu J, Dong G, Jin C, Huang M, Guan L. Sulfur and nitrogen co-doped, few-layered graphene oxide as a highly efficient electrocatalyst for the oxygen-reduction reaction. *ChemSusChem* 2013;6:493–9.
- [6] Xiang Q, Yu J, Jaroniec M. Graphene-based semiconductor photocatalysts. *Chem Soc Rev* 2012;41:782–96.
- [7] Wang X, Li X, Zhang L, Yoon Y, Weber PK, Wang H, et al. N-doping of graphene through electrothermal reactions with ammonia. *Science* 2009;324:768–71.
- [8] Garcia-Gallastegui A, Iruretagoyena D, Gouvea V, Mokhtar M, Asiri AM, Basahel SN, et al. Graphene oxide as support for layered double hydroxides: enhancing the CO<sub>2</sub> adsorption capacity. *Chem Mater* 2012;24:4531–9.
- [9] Guo CX, Yang HB, Sheng ZM, Lu ZS, Song QL, Li CM. Layered graphene/quantum dots for photovoltaic devices. *Angew Chem Int Ed* 2010;49:3014–7.
- [10] Zhao G, Jiang L, He Y, Li J, Dong H, Wang X, et al. Sulfonated graphene for persistent aromatic pollutant management. *Adv Mater* 2011;23:3959–63.
- [11] Wang H-X, Wang Q, Zhou K-G, Zhang H-L. Graphene in light: design, synthesis and applications of photo-active graphene and graphene-like materials. *Small* 2013;9:1266–83.
- [12] Sui Z, Meng Q, Zhang X, Ma R, Cao B. Green synthesis of carbon nanotube-graphene hybrid aerogels and their use as versatile agents for water purification. *J Mater Chem* 2012;22:8767–71.
- [13] Dong Z, Jiang C, Cheng H, Zhao Y, Shi G, Jiang L, et al. Facile fabrication of light, flexible and multifunctional graphene fibers. *Adv Mater* 2012;24:1856–61.
- [14] Bai H, Li C, Wang X, Shi G. On the gelation of graphene oxide. *J Phys Chem C* 2011;115:5545–51.
- [15] Lee JS, You KH, Park CB. Highly photoactive, low bandgap TiO<sub>2</sub> nanoparticles wrapped by graphene. *Adv Mater* 2012;24:1084–8.
- [16] Chandra V, Park J, Chun Y, Lee JW, Hwang I-C, Kim KS. Water-dispersible magnetite-reduced graphene oxide composites for arsenic removal. *ACS Nano* 2010;4:3979–86.

- [17] Wu X-L, Wang L, Chen C-L, Xu A-W, Wang X-K. Water-dispersible magnetite-graphene-LDH composites for efficient arsenate removal. *J Mater Chem* 2011;21:17353–9.
- [18] Mathieu Y, Tzani L, Soulard M, Patarin J, Vierling M, Molière M. Adsorption of SO<sub>x</sub> by oxide materials: a review. *Fuel Process Technol* 2013;114:81–100.
- [19] Chandra Srivastava V. An evaluation of desulfurization technologies for sulfur removal from liquid fuels. *RSC Adv* 2012;2:759–83.
- [20] Gates BC, Topsøe H. Reactivities in deep catalytic hydrodesulfurization: challenges, opportunities, and the importance of 4-methylthiophene and 4,6-dimethylthiophene. *Polyhedron* 1997;16:3213–7.
- [21] Hernández-Maldonado AJ, Yang RT. Desulfurization of transportation fuels by adsorption. *Catal Rev* 2004;46:111–50.
- [22] Achmann S, Hagen G, Hämmerle M, Malkowsky IM, Kiener C, Moos R. Sulfur removal from low-sulfur gasoline and diesel fuel by metal-organic frameworks. *Chem Eng Technol* 2010;33:275–80.
- [23] Haji S, Erkey C. Removal of dibenzothiophene from model diesel by adsorption on carbon aerogels for fuel cell applications. *Ind Eng Chem Res* 2003;42:6933–7.
- [24] Bu J, Loh G, Gwie CG, Dewiyanti S, Tasrif M, Borgna A. Desulfurization of diesel fuels by selective adsorption on activated carbons: competitive adsorption of polycyclic aromatic sulfur heterocycles and polycyclic aromatic hydrocarbons. *Chem Eng J* 2011;166:207–17.
- [25] Duan F, Chen C, Wang G, Yang Y, Liu X, Qin Y. Efficient adsorptive removal of dibenzothiophene by graphene oxide-based surface molecularly imprinted polymer. *RSC Adv* 2014;4:1469–75.
- [26] Samokhvalov A, Tatarchuk BJ. Review of experimental characterization of active sites and determination of molecular mechanisms of adsorption, desorption and regeneration of the deep and ultradeep desulfurization sorbents for liquid fuels. *Catal Rev* 2010;52:381–410.
- [27] Shen Y, Li P, Xu X, Liu H. Selective adsorption for removing sulfur: a potential ultra-deep desulfurization approach of jet fuels. *RSC Adv* 2012;2:1700–11.
- [28] Liu Y, Guo F, Hu J, Zhao S, Liu H, Hu Y. Screening of desulfurization adsorbent in metal-organic frameworks: a classical density functional approach. *Chem Eng Sci* 2015;137:170–7.
- [29] Liu Z, Ma R, Osada M, Iyi N, Ebina Y, Takada K, et al. Synthesis, anion exchange, and delamination of Co–Al layered double hydroxide: assembly of the exfoliated nanosheet/polyanion composite films and magneto-optical studies. *J Am Chem Soc* 2006;128:4872–80.
- [30] Iruretagoyena D, Shaffer MP, Chadwick D. Adsorption of carbon dioxide on graphene oxide supported layered double oxides. *Adsorption* 2014;20:321–30.
- [31] Iruretagoyena D, Shaffer MSP, Chadwick D. Layered double oxides supported on graphene oxide for CO<sub>2</sub> adsorption: effect of support and residual sodium. *Ind Eng Chem Res* 2015;54:6781–92.
- [32] Rourke JP, Pandey PA, Moore JJ, Bates M, Kinloch IA, Young RJ, et al. The real graphene oxide revealed: stripping the oxidative debris from the graphene-like sheets. *Angew Chem Int Ed* 2011;50:3173–7.
- [33] Xiong L, Chen F-X, Yan X-M, Mei P. The adsorption of dibenzothiophene using activated carbon loaded with cerium. *J Porous Mater* 2012;19:713–9.